

The Nature of Vibrations of a 2-D Disordered Lattice Model with Nano-scale Order

Prasenjit Ghosh and Umesh V Waghmare

*Theoretical Sciences Unit,
Jawaharlal Nehru Centre for Advanced Scientific Research,
Jakkur PO, Bangalore 560 064, India*

Motivated by the unusual soft mode anomalies in the relaxor ferroelectrics, we present a numerical study of vibrational excitations of a disordered lattice model with chemical order on the nano-scale. We find an Ioffe-Regel crossover in acoustic modes separating propagating low-frequency modes from the intermediate frequency diffusons, and localized modes at the high-frequency end of the spectrum. At a fixed degree of disorder, we find increasing uncertainty in the momentum of long wave-length optical modes with decrease in the size of nano-ordered regions. We determine the cause for this to be a strong mixing between acoustic and optical modes, believed to be central to the model of waterfall phonon anomalies.

PACS numbers: 63.22.+m 63.20.Dj 74.25.Kc

Nano-scale structure of materials has interesting effects on their macroscopic behavior and become yet another control parameter in tuning material properties[1]. For example, relaxor ferroelectrics, such as $\text{PbMg}_{1/3}\text{Nb}_{2/3}\text{O}_3$ (PMN)[2] and $\text{PbSc}_{1/2}\text{Nb}_{1/2}\text{O}_3$ (PSN)[3], have tremendous technological potential in applications based on solid state transducers[4], due to their giant electromechanical and dielectric response. Randomness and nano-scale regions in the ordering of polar fields are known to be central to these interesting properties[5, 6]. In contrast to conventional ferroelectrics such as PbTiO_3 with a sharp ferroelectric transition, relaxors exhibit a diffuse ferroelectric transition, with a broad peak in dielectric constant as a function of temperature.

Ferroelectricity in conventional ferroelectric materials is essentially a phonon-related property characterized by a soft mode near the ferroelectric phase transition[7, 8]. The soft phonon anomalies in the context of relaxors[9] were observed as “waterfall phonons” recently using neutron scattering, with a speculation that these are linked with nano-polar regions. Further studies of the “waterfall” phenomena based on neutron scattering were explained using a mode-coupling theory[10, 11] for the coupling between acoustic and optical modes. While the work of Hlinka et al [11] argued that the wave-vector k of the waterfall phonon is unlikely to be related to the size of nano-polar regions, the origin of coupling between acoustic and optical modes is not known.

A relaxor, for example PSN, PST etc., is a solid solution with a degree of disorder arising from the chemical ordering of Sc and Nb (for PSN) and Sc and Ta (for PST) at the B sites of ABO_3 perovskite lattice. Correlation between such disorder and relaxor properties of PSN and PST were shown experimentally[3, 12]. A region of the size of $\approx 2\text{-}6\text{ nm}$ [13, 14, 15] with a specific kind of chemical ordering defines a nano-ordered region (NOR) with intense local polar fields[6, 16]. Through the coupling with ferroelectric dipoles, they give rise to nano-polar regions (NPR), speculated to be linked with

phonon anomalies called “waterfall phonons” in relaxors. Precise knowledge of the nature of phonons in the presence of chemically nano-ordered regions is essential to establish their possible link with the “waterfall phonons”.

In this letter, we determine the nature of vibrational excitations in a model system which consists of chemically-ordered nano-regions in a percolating disordered matrix. While the model used in our analysis is a great simplification of relaxors, it allows us to determine some general aspects of phonons in a nano-ordered system. In particular, we find localization of modes at high frequencies and an Ioffe-Regel crossover at low frequencies, similar to that found in amorphous systems[17, 18, 19]. Our findings about the nature of long-wavelength optical modes helps in uncovering possible links between nano-scale order and waterfall phonons in terms of the mode coupling analysis of Hlinka *et al*[11].

For the ordered case, our model system consists of two types of atoms A and B occupying $(0,0)a$ and $(\frac{1}{2}, \frac{1}{2})a$ sites of a square lattice respectively, a being the lattice constant. The interaction between two atoms displaced from their mean position by $\mathbf{u}_i$ and $\mathbf{u}_j$ is given by

$$U_{ij} = k_L(\hat{\mathbf{b}}_{\parallel} \cdot \mathbf{u}_i)(\hat{\mathbf{b}}_{\parallel} \cdot \mathbf{u}_j) + k_T(\hat{\mathbf{b}}_{\perp} \cdot \mathbf{u}_i)(\hat{\mathbf{b}}_{\perp} \cdot \mathbf{u}_j) \quad (1)$$

where $\hat{\mathbf{b}}_{\parallel}$ and $\hat{\mathbf{b}}_{\perp}$ are the unit vectors parallel (longitudinal) and perpendicular (transverse) to the line joining two atoms respectively, k_L and k_T being the longitudinal and transverse force constants respectively. Only harmonic interactions up to the second nearest neighbors $((1,1)a)$ have been included, giving 10 distinct interatomic force constants $k_{L,T}^{AAnn}$, $k_{L,T}^{AA2nn}$, $k_{L,T}^{BBnn}$, $k_{L,T}^{BB2nn}$, $k_{L,T}^{ABnn}$ and two onsite interactions k_A and k_B , where nn and $2nn$ stand for the nearest and next nearest neighbors respectively. Values of the force constants (Table I) have been chosen such that the acoustic sum rule is obeyed, there are stable modes throughout the Brillouin zone, and acoustic and optical branches are well-separated.

Disorder is introduced by randomly selecting two different types of atoms and interchanging their positions

making sure that a given atom is interchanged only once. A configuration with nano-scale order is obtained by excluding such an interchange in the circular nano-ordered regions (NORs) with a fixed diameter of a few nanometers. Centres of these circular regions are taken randomly, but avoiding any overlap between them. The degree of disorder is quantified with a disorder parameter δ defined as

$$\delta = \frac{\text{No. of A-A or B-B nearest neighbors}}{\text{Total no. of nearest neighbor}}. \quad (2)$$

For a fully ordered case, $\delta = 0.0$, whereas δ is 0.5 for the completely disordered case. For a disordered configuration A and B occupy one of the two sites of the square lattice with equal probability, resulting in new types of neighboring pairs of atoms, such as (A-B)_{2nn} and (A-B)_{3nn}. The force constants for their interactions are taken as $(k_X^{AAnn} + k_X^{BBnn})/2.0$ and $(k_X^{AA2nn} + k_X^{BB2nn})/2.0$ respectively, where $X = L, T$. Similarly, nearest neighbor atoms of the same type can possibly be separated by $(0.5, 0.5)a$, for which the force constants are given by $k_{X,disorder}^{YYnn} = 2 k_X^{YY2nn}$, where $Y = A, B$. The $(Y-Y)_{nn}$ and $(Y-Y)_{2nn}$ interactions for the ordered case are now the $(Y-Y)_{2nn}$ and $(Y-Y)_{3nn}$ respectively. The acoustic sum rule is imposed by correcting the diagonal elements of the force constant matrix[20]. Using this model, we study vibrational modes of configurations consisting of 32×32 lattice sites (2048 atoms) with different number of nano-ordered regions and $\delta \approx 0.4$.

TABLE I: Force constants (in ar. units) for different interactions along different directions

Force Constants	Values	Force Constants	Values
k_A	19.0	k_L^{BBnn}	-2.5
k_B	16.0	k_T^{BBnn}	-0.5
k_L^{AAnn}	-2.0	k_L^{BB2nn}	-0.25
k_T^{AAnn}	-0.5	k_T^{BB2nn}	0.0
k_L^{AA2nn}	-1.25	k_L^{ABnn}	-2.25
k_T^{AA2nn}	0.0	k_T^{ABnn}	-1.25

The spectral density function ($S_k(\omega)$) is calculated for different configurations, which allows us to relate to the constant energy scan and constant momentum transfer scan obtained in the neutron scattering experiments. We use the contour plot of $S_k(\omega)$ in visualizing the dispersion of phonon modes for systems with disorder. The spectral density function[21] is given by

$$S_k(\omega) = \frac{\sum_{j=1}^{2N} |\bar{\alpha}_{\mathbf{k}}^j|^2 \delta(\omega - \omega^j)}{2N} \quad (3)$$

where N is the total number of atoms. ω^j is the frequency of the j^{th} eigenmode, $|\bar{\alpha}_{\mathbf{k}}^j|$ is the Fourier transform of the

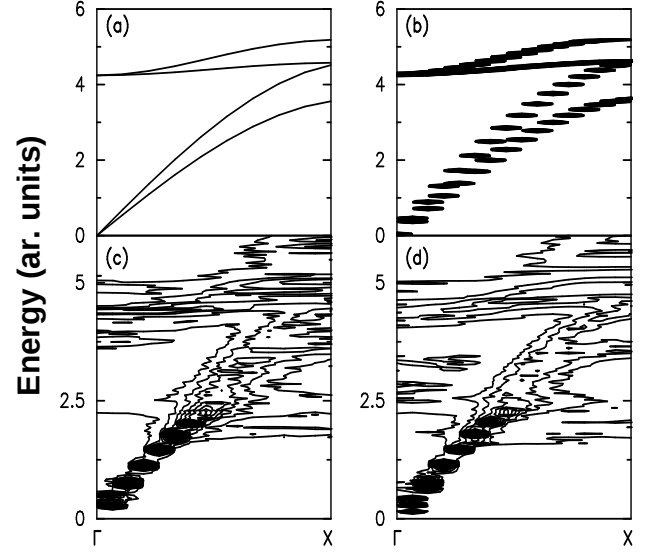


FIG. 1: Phonon dispersion obtained from (a) the dynamical matrix of ordered system, and (b, c, d) contour plots of $S_k(\omega)$ for the ordered system, a nano-ordered system with fourteen NORs each of radius $\approx 2.2 a$ and a fully disordered system respectively.

real space eigenvector of the j^{th} mode. Phonon dispersion of the ordered system along the $\langle 10 \rangle$ direction obtained from dynamical matrix and from $S_k(\omega)$ are compared in Fig. 1. At X point, the longitudinal optical branch has the highest energy, whereas the transverse optical branch is degenerate with the longitudinal acoustic branch. Finite width of the peaks in the contour plot of $S_k(\omega)$ arise from the width of Gaussian used to approximate the delta function in Eqn (3). Based on a reasonable agreement between the two descriptions, we use $S_k(\omega)$ -based description in the study of phonons of systems with disorder. Our results for phonons of nano-ordered and disordered configurations (Fig. 1(c)-(d)) show that the introduction of disorder results in mixing of the phonon modes and subsequent broadening of peaks in $S_k(\omega)$ as a function of both k and ω , k is no longer a good quantum number to describe these modes. While new modes with intermediate energies appear near the Γ point, long wavelength acoustic modes for $k \lesssim 0.22$ are least affected. This is consistent with the error-bars on phonon measurements using inelastic neutron scattering technique[9].

To probe extended versus localized nature of modes in the presence of disorder and nano-ordered regions we calculate inverse participation ratio (IPR):

$$IPR(\omega_j) = N \frac{\sum_i |\bar{\alpha}_i^j|^4}{(\sum_i |\bar{\alpha}_i^j|)^2}, \quad (4)$$

where $\bar{\alpha}^j$ are the eigenstates of the phonon modes. IPR is N (1) for a fully localized (extended) mode. For a configuration with fourteen nano-ordered regions, IPR as a function of energy (Fig. 2(a)) is found to be quite similar

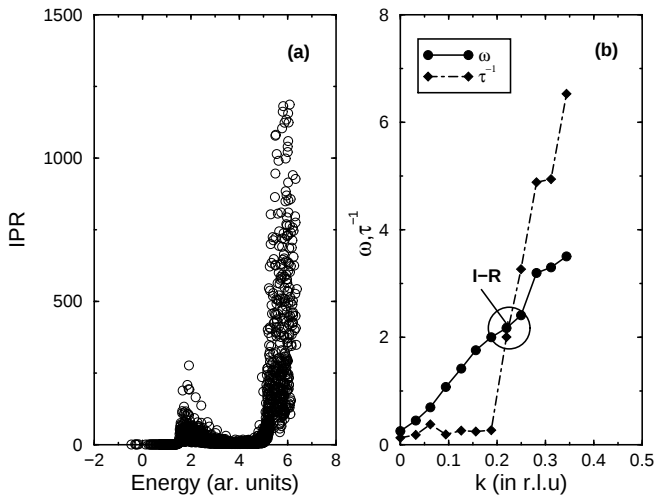


FIG. 2: For the configuration with 14 NORs: (a) IPR as a function of energy and (b) acoustic mode frequency and its inverse decay time as a function of wavevector, point of their crossover is indicated by a circle.

to that obtained for amorphous Si[18]. The high energy modes, between 5.0 and 6.0 units of energy, are highly localized and are called locons, while the rest are called extendons[18]. Some modes around $\epsilon = 2.0$ have intermediate values of IPR exhibiting moderate localization. We investigated these modes further by examining distribution of number of atoms as a function of their contribution to the IPR and find that they are similar to the localized modes with the same IPR and $5 < \epsilon < 6$. However, the former have non-negligible character of long-wavelength modes (evident in Fig 1) and the latter do not.

Extendons can be classified into two categories, the propagons (these propagate ballistically) and the diffusons. Wave vector k is a good quantum number for propagons, but not for diffusons. The Ioffe-Regel (I-R) cross-over [17] separates propagons and diffusons as a function of frequency. In the frequency domain, the full width at half maxima (ζ) of a peak in the spectral density function is used to obtain the decay time τ of a propagating mode due to scattering ($\tau_k^{-1} \simeq \pi\zeta_\omega(k)$)[19]. The crossover point between ω vs. k and τ^{-1} vs. k gives the location (k) of the I-R cross-over. For the configuration with fourteen nano-ordered regions (Fig. 2(b)), we find the I-R crossover at $k = 0.22$ r.l.u. and $\omega = 2.2$. The vibrational modes with energy between 2.2 and 5.0 are thus diffusons.

To further affirm this classification of modes, we studied their level spacing distribution (LSD). LSD, with its foundation in the random matrix theory (RMT), is known to exhibit Wigner-Dyson statistics for diffusons and Poisson statistics for locons [18]. We calculated level spacings distribution using *spectral unfolding*, in which the original spectrum is mapped into an ordered set of

numbers with uniform density of states. We find that the LSD for modes with $2.2 < \epsilon < 5.0$ obeys Wigner-Dyson statistics whereas that for modes with $\epsilon > 5.0$ obeys Poisson statistics with slight deviation near zero spacing. This supports our classification of these modes as diffusons and locons respectively.

To explore mixing among phonon modes due to disorder, we introduce an energy correlation function $f(\epsilon, \epsilon')$ as an overlap between the modes of the ordered system ($|\alpha_n^O\rangle$) with those of the disordered system ($|\alpha_m^D\rangle$):

$$f(\epsilon, \epsilon') = \sum_{m,n} |\langle \alpha_m^D | \alpha_n^O \rangle|^2 \delta(\epsilon - \epsilon_m) \delta(\epsilon' - \epsilon_n). \quad (5)$$

It is based on the representation of modes of a disordered configuration as a linear combination of normal modes of a fully ordered system. The contour plots of $f(\epsilon, \epsilon')$ (Fig. 3) clearly show that the acoustic modes of a nano-ordered system in the IR-crossover region emerge from mixing of acoustic and optical modes of the ordered system. At the fixed degree of disorder, this mixing becomes stronger with the number of nano-ordered regions. Secondly, diffuson modes in the optical region of the spectrum of a nano-ordered system arise mainly from mixing among optical modes with different wave vector. We find that the effects of disorder become stronger as the number (size) of nano-ordered regions increases (decreases).

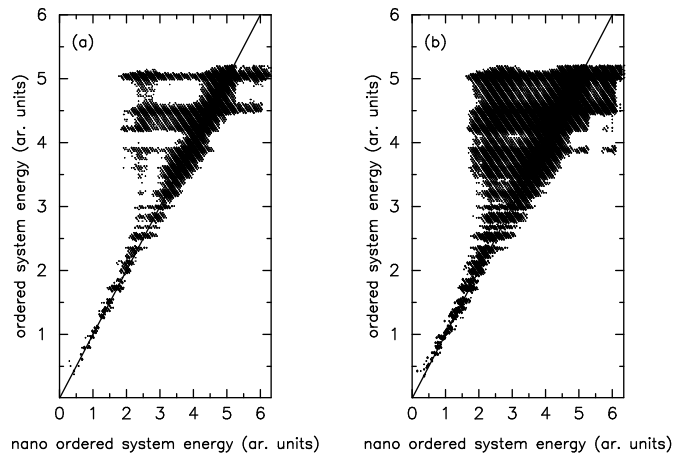


FIG. 3: Energy correlation between the modes of ordered system and that of a configuration having (a) 8 nano-ordered regions and (b) 14 nano-ordered regions. The straight line shows perfect correlation or NO mixing.

To understand the nature of diffusons, we show in Fig. 4 the k -dependence of $S_\omega(k)$ for $\omega \simeq 4.292 \pm 0.034$ corresponding to peaks of S at the Γ point for a given configuration. It shows that the probability of finding a long wavelength optical mode decreases as the number of nano-ordered regions increases, as many of these degrees of freedom precipitate into the acoustic branches due to strong mixing. Correspondingly, the uncertainty in momentum $\hbar k$, which is given by the full width at half maximum (FWHM) of a peak in spectral-density also

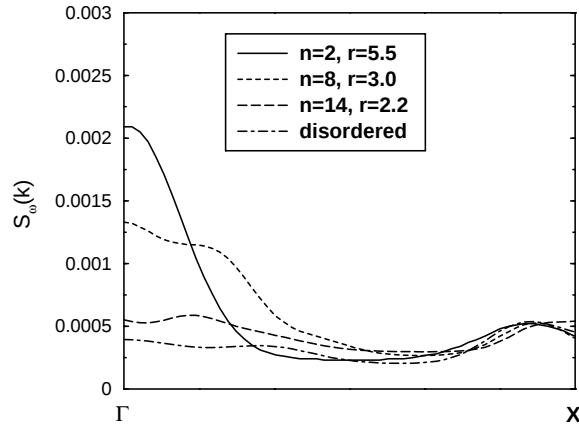


FIG. 4: Probability of finding an optical mode in the long wavelength limit. “n” denotes the no. of nano-ordered regions present in the system and “r” is the radius of each nano-ordered region. These modes have energy $\omega=4.292\pm0.034$ units.

increases. For configurations having fourteen or more nano-ordered regions, there is no well-defined peak for which the FWHM can be estimated.

Due to scattering from chemical disorder, optical modes (propagons) of the ordered system become diffusive. We suggest that the diffusons should be relevant to the diffuse dynamical properties of relaxors or diffuse phase transition behavior in ferroelectrics. While the phonons considered here are hard (high frequency) and treated within harmonic approximation, those in real ferroelectrics are soft and exhibit strong anharmonicity. Scattering of soft modes due to disorder is expected to be even stronger and their anharmonicity will lead to scattering among phonons. As the present work is on a 2-D system and some of its features are likely to be qualitatively different in 3-D, precise implications for the real relaxors need further investigation.

In connection with the waterfall phonon anomaly, our results show that nano-ordered regions of large enough size *are* essential for the observation of phonons with a definite wave-vector. Secondly, their size does affect the strength of mixing between optical and acoustic modes, though not the wavevector corresponding to the I-R crossover. The former is the basis of mode-coupling theory and latter is consistent with the conclusion of Hlinka *et al*[11]. We note that the NPR’s (not NORs) are present in conventional ferroelectrics too (like the chain-like dynamic polar distortions in KNbO_3 [22]) over a narrow temperature range above T_c and “waterfall phenomenon” should be more general. As the acoustic modes essentially span configurations with inhomogeneous strain, the coupling of inhomogeneous strain with polar optical modes seems to be the common origin of “waterfall phonons” and also the relaxor dynamics[23].

In summary, we find that chemical disorder on a 2-D lattice results in phonon modes of type: propagons, diffusons and locons. At the fixed degree of disorder, reduction in the size of nano-ordered regions results in increase (decrease) in the width (height) of peaks corresponding to long wavelength optical modes as a function of k . This correlates with corresponding increase in the mixing between optical and acoustic modes. While the length-scale of chemical ordering needs to be large enough (a few nano-metre) for observing optical phonon modes with a definite momentum, it also has to be small to give adequate mixing with acoustic modes responsible for the “waterfall phonons”.

We thank Chandrabhas Narayan, Ranjith and Srikanth Sastry for useful discussions. UVW acknowledges a DuPont young faculty award and PG acknowledges CSIR, India for a research scholarship.

-
- [1] S. Seal and M.-I. Barton, MRS Bulletin **29**, 9 (2004).
 - [2] L. E. Cross, Ferroelectrics **76**, 241 (1987).
 - [3] F. Chu, I. M. Reaney and N. Setter, J. App. Phys, **77**, 1671 (1995).
 - [4] R. F. Service, Science **275**, 1878 (1997).
 - [5] R. Pirc and R. Blinc, Phys. Rev. B **60**, 13470 (1999).
 - [6] V. Westphal, W. Kleemann and M. D. Glinchuk, Phys. Rev. Lett. **68**, 847 (2000).
 - [7] W. Cochran, Adv. Phys. **10**, 401 (1961)
 - [8] P. W. Anderson, Fizika Dielektrikov (ed. G. I. Skanavi), Akad. Nauk USSR, Moscow (1960).
 - [9] P. M. Gehring, S.-E. Park, and G. Shirane, Phys Rev. Lett. **84**, 5216 (2000).
 - [10] P. M. Gehring, S.-E. Park, and G. Shirane, Phys. Rev. B **63**, 224109 (2001).
 - [11] J. Hlinka *et al.*, Phys Rev. Lett. **91**, 107602 (2003).
 - [12] N. Setter and L. E. Cross, J. Appl. Phys. **51**, 4356 (1980).
 - [13] H.B. Krause, J.M. Cowley and J. Wheatley, Acta. Cryst. **A35** 1015 (1979).
 - [14] C. Perrin *et al.*, J. Phys. Condens. Matter, **13** 10231 (2001).
 - [15] H.Z. Jin *et al.*, J. App. Phys, **89** 5048 (2001).
 - [16] H. Quian and L.A. Bursill, Int. J. of Mod. Phys. **10**, 2027 (1996).
 - [17] A. F. Ioffe and A. R. Regel, Prog. Semicond. **4**, 237 (1960).
 - [18] P. B. Allen *et al.*, Phil. Mag. B **79**, 1715 (1999).
 - [19] S. N. Taraskin and S. R. Elliot, Phys. Rev. B **61**, 12031 (2000).
 - [20] X. Gonze, Phys. Rev. B **55**, 10337 (1997).
 - [21] H. Ehrenreich and L. M. Schwartz, in *Solid State Physics*, edited by H. Ehrenreich, F. Seitz, and D. Turnbull (Academic, New York, 1976), Vol. 31, p. 149.
 - [22] H. Krakauer *et al.*, J. Phys: Cond. Matt. **11**, 3779 (1999).
 - [23] M. Glinchuk, A. Morozovska and E. Eliseev, Integrated Ferroelectrics **64**, 17 (2004).